

DEVELOPMENT OF STONE MASTIC ASPHALT MIXES FOR ONTARIO USE

JOHN CARRICK AND KEITH MACINNIS
President and Technical Services Manager, Respectively
McAsphalt Industries Limited
West Hill (Toronto) Ontario

and

KEITH DAVIDSON, WALTER SCHENK AND JOHN EMERY
Principal Asphalt Engineer, Asphalt Technology Advisor,
and President, Respectively
John Emery Geotechnical Engineering Limited
Downsview (Toronto) Ontario

ACKNOWLEDGEMENTS

Stone mastic asphalt (SMA) mix design and production information provided by Masahiko Ishitani (Taisei Road Construction Co., Ltd.) and Ottmar Schütz (Wilh. Schütz KG Construction) was particularly helpful in the SMA technology transfer to Ontario. The continuing logistical and technical support of the Ontario Ministry of Transportation (Gerhard Kennepohl, Manager of Pavements and Roadway Research) with SMA highway trial sections and testing is gratefully acknowledged. Johanna Ernyes' assistance with mix designs at McAsphalt Engineering Services is also gratefully acknowledged.

ABSTRACT

Stone mastic asphalt mix (SMA) use in Europe (split mastic in Germany) and Japan, based on excellent frictional properties, plastic deformation resistance, fatigue endurance and durability, formed the basis for recent technology transfer demonstration trials. The thrust of this SMA work has been to incorporate international experience using local aggregates, fillers, engineered asphalt cement and fibre. SMA is a gap-graded, dense, hot-mix asphalt with a large proportion of coarse aggregate (passing 2 mm limited to about 20 percent, all crushed material) and a rich asphalt cement/filler mastic. The coarse aggregate forms a high stability structural matrix and the engineered asphalt cement, fine aggregate, filler and stabilization additive (typically fibre) form a mastic binding the structural matrix together. Plant and placement trials of preliminary SMA designs (0/19 mm and 0/13 mm) incorporating engineered asphalt cement, fly ash filler and fibre indicated no transportation, placement or compaction problems, but care must be taken to ensure proper mixing of any fibre added. From this demonstration work, SMA mix design procedures have been developed and a series of highway test sections initiated. Full characterization of SMA pavements is planned, including Nottingham Asphalt Tester use.

RESUMÉ

Le mastic bitumineux à la pierre (SMA) utilisé en Europe (mastic discontinu en Allemagne) et au Japon, et qui présente d'excellentes propriétés de frottement, une résistance à la déformation plastique et à la fatigue et une durabilité, constitue la base des essais récents de transferts technologique. Le but de la recherche sur le mastic bitumineux à la pierre était d'intégrer l'expérience internationale en utilisant des granulats locaux, des fillers, du ciment asphaltique modifié et des fibres.

Le mastic bitumineux à la pierre est un asphalte dense mélangé à chaud et à granulométrie discontinue contenant une part importante de granulats grossiers (environ 20% avec un diamètre ≤ 2 mm, tous matériaux concassés) et une mastic riche en bitume et en filler. Les granulats grossiers forment un mastic donnant une structure de forte stabilité; le ciment asphaltique modifié, les granulats fins, le filler et le mélange de stabilisation (surtout des fibres) forment quant à eux un mastic liant la structure.

Les essais en usine et sur le terrain des premiers mélanges de mastic bitumineux à la pierre (0/19 mm et 0/13 mm) qui contenaient du ciment asphaltique modifié, un filler de cendres volantes et des fibres n'ont indiqué aucune problème de transport, d'application et de compactage. Il faut cependant bien mélanger toutes les fibres ajoutées. A partir de ces essais, on a entrepris une série d'essais sur des sections de route. On planifie une présentation complète des chaussées fabriquées avec le mastic bitumineux à la pierre, y compris l'utilisation du "Nottingham Asphalt Tester".

INTRODUCTION

With the growing use of stone mastic asphalt (SMA) in Europe and Japan, and the obvious technology transfer applicability to Canada in terms of both climate and pavement performance requirements, an SMA research and development team (a) approach was used to quickly complete demonstration SMA trial sections in December 1990, the first in North America. This initial satisfactory SMA demonstration work was then extended to an SMA highway test section in June 1991 assisted by the Ontario Ministry of Transportation (MTO), with testing, further SMA mix designs and additional highway test sections in progress. The use of SMA in Europe and Japan is based on demonstrated excellent frictional properties, plastic deformation (rutting) resistance, fatigue endurance and durability. The thrust of the team's SMA work has been to incorporate international SMA design and construction experience using locally available aggregates, fillers, engineered asphalt cement and fibres in conventional hot-mix plants.

STONE MASTIC ASPHALT (SMA)

What is stone mastic asphalt (SMA) and why is it getting so much attention from North American pavement experts [1-4]? SMA (termed split mastic in Germany where it has been developed and used for about twenty years) is a gap-graded, dense (about 3 percent air voids mix design), hot-mix asphalt with a large proportion of coarse aggregate (passing 2 mm limited to about 20 percent, all aggregate 100 percent crushed) and a rich asphalt cement/filler mastic (about 10 percent minus 75 μm) [5,6]. The coarse aggregate, through point-to-point contact as shown schematically in Figure 1, forms a high stability skeleton (structural matrix) with good internal friction and aggregate interlock to resist load-induced shear. A typical SMA grading band, compared to conventional hot-mix asphalt (HMA) is given in Figure 2 with further details on typical SMA aggregates and filler compositions.

The asphalt cement (typically polymer-modified), fine aggregate, filler and stabilization additive (if necessary, typically about 0.3 percent mineral, glass or cellulosic fibre to prevent asphalt cement runoff) form a mastic binding the structural matrix together. The polymer modified asphalt cement content is typically 1.0 to 1.5 percent greater than for a conventional HMA incorporating the same aggregates. This rich, durable mastic has a far higher filler (finer than 90 μm) to asphalt cement content ratio than the limit of 1.2 recommended by the Federal Highway Administration (FHWA) for conventional dense graded HMA [7]. The SMA's high stability skeleton must contain all the mastic binder while maintaining the point-to-point contacts (Figure 1) essential for shear deformation (rutting) resistance. SMA is usually designed to have an air voids content of 3 percent. Too much mastic will push the coarse aggregate particles apart with a drastic reduction in pavement shear deformation resistance, while too little mastic

a The SMA research and development team consists of McAsphalt Industries Limited (logistics and mix designs), Miller Paving Limited (production and placement) and John Emery Geotechnical Engineering Limited (engineering and quality assurance).

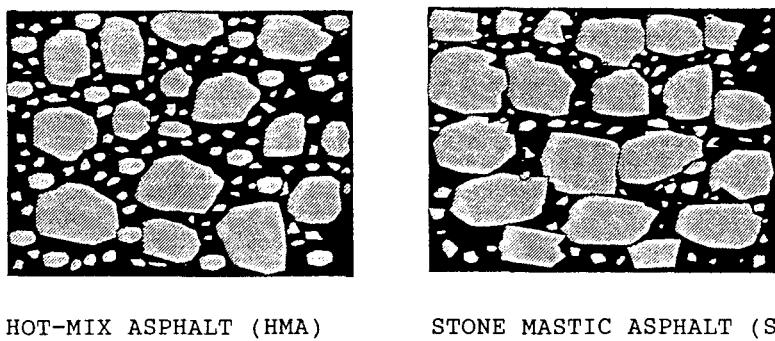


FIGURE 1. COMPARISON OF 'FLOATING' COARSE AGGREGATE IN HMA WITH STONE-TO-STONE 'SKELETON' IN SMA.
 (The point-to-point contact achieved in the SMA provide internal friction to resist load-induced shear. Adapted from Report on the 1990 European Asphalt Study Tour (EAST) [6].)

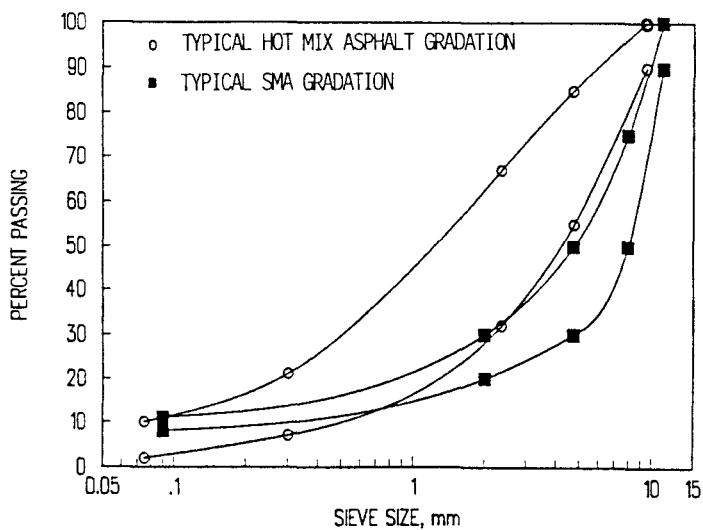


FIGURE 2. COMPARISON OF TYPICAL DENSE GRADED HOT-MIX ASPHALT (HMA) AND STONE MASTIC ASPHALT (SMA) GRADING BANDS.

(Coarse aggregate (plus 2 mm) about 70 to 80 percent, fine aggregate (2 mm to 90 μm) about 12 to 17 percent and filler (minus 90 μm) about 8 to 13 percent for SMA. SMA coarse aggregate top size typically between 11 and 16 mm. Adapted from Report on the 1990 European Asphalt Study Tour (EAST) [6].)

will result in high air voids with reduced pavement durability due to accelerated aging and moisture damage [5,6]. Obviously, there is little latitude during SMA production in the mix design, aggregate gradation, polymer modified asphalt cement content or fibre content.

The SMA typical mix design (50 blow Marshall method often used [8-10]) air voids content of 3 percent provides an in-place air voids content of less than 6 percent. Static steel-wheel compaction is used primarily to orient the coarse aggregate particles at the pavement surface and there is little additional roller densification or deformation. To avoid coarse aggregate fracture, vibratory rolling is not used, and to avoid possible mastic surface flushing, pneumatic rolling is not used. Since there is little compaction densification of SMA, the mastic must be rich in asphalt cement (binder) to achieve the low in-place voids essential to durability.

After placement and compaction, SMA has a coarse (open) surface texture characterized by good coarse aggregate macro-texture (large, rough depressions) that provides excellent frictional properties ('skid' resistance) over time. However, with the rich mastic involved, there may be a period of traffic action required to wear the binder film off the coarse aggregate in order to develop microtexture. If this is of concern, an asphalt cement pre-coated sand or hot sand application can be used to provide enhanced frictional properties until microtexture is developed.

By modifying the gradation to essentially a single-size coarse aggregate, a free-draining (porous) asphalt mix (porous asphalt, PA) can also be developed for open friction course applications. Porous asphalt (PA) mix designs have been developed by the team and it is anticipated that some PA trial sections will be completed and reported in 1992.

A comparison of SMA and PA properties and features with those of conventional HMA is given in Table 1, which is based on Nordic experience. In summary, SMA has excellent wear and frictional properties, plastic deformation (rutting) resistance, fatigue endurance, resistance to low temperature cracking and durability, all critical attributes for thin, surface course asphalt paving and high traffic density routes.

SUMMARY OF EUROPEAN AND JAPANESE EXPERIENCE WITH SMA

A review of practical experience with SMA in Denmark, Finland, Germany, Netherlands, Norway, Sweden and Japan [5,6,8,9, Wilh. Schütz and Taisei] indicated the following typical features and practices:

Reasons for Use

1. high stability (resistance to rutting) combined with good durability (20 to 40 percent longer life than conventional mixes)
2. good resistance to studded tire wear
3. good frictional properties (skid resistance)
4. thin surface course use allows relatively low costs
5. good placement and compaction characteristics

Reasons for Not Using

1. costs
2. lack of knowledge with new mix type

Hot-Mix Technology

1. mix design air voids of 3 to 4 percent, typically 3 percent
2. Marshall method of mix design (50 blows each face at 135°C) sometimes used with design at 3 percent air voids
3. all aggregates 100 percent crushed with suitable frictional properties (high quality aggregates)
4. coarse aggregate content 70 percent
5. maximum coarse aggregate size of 5 to 20 mm, typically 11 to 16 mm
6. mortar
 - a. asphalt cement content 6.5 to 8 percent
 - b. filler content 8 to 13 percent
 - c. fibre content 0.3 to 1.5 percent (mineral, glass or cellulosic fibre - fibre not used in some high polymer loaded mixes)
7. asphalt cement
 - a. range of penetration grades - 65, 80, 200
 - b. polymer modified 80 penetration grade seems typical

TABLE 1. RANKING OF STONE MASTIC ASPHALT (SMA) AND POROUS ASPHALT (PA) COMPARED WITH HOT-MIX ASPHALT (HMA) (a).

PROPERTY OR FEATURE	RANKING COMPARED TO HMA (b)	
	SMA	PA
Shear Resistance	2	2
Abrasion Resistance	2	-½
Durability	2	-1½
Load Distribution	-½	-1½
Cracking Resistance	1½	-½
Skid Resistance	1	1½
Water Spray	0	3
Light Reflection	1	1½
Noise Reduction	0	3
Public Recognition	2	3

a. Adapted from ranking by Nordic asphalt technologists given in Report on the 1990 European Asphalt Study Tour (EAST) [6].

b. Ranking Scale: 0 Equal
 1 Better -1 Worse
 2 Much Better -2 Much Worse.
 3 Very Much Better

Production and Placement

1. increased dry mixing time to allow for fibre dispersion
2. easier to place and compact than conventional mixes, especially in thin lifts
3. less sensitive to laying failure
4. use static steel-wheel compaction (avoid vibratory and pneumatic compaction)

Mechanical Properties

1. good resistance to plastic deformation (rutting) from wheel tracking tests
2. stiffness modulus and fatigue resistance not determined

Trends

1. expected to take the place of dense graded asphaltic concrete
2. will be more economic in long term because of better durability, stability, fatigue resistance and workability.

This type of information on SMA and the practical advice of Taisei and Wilh. Schütz was particularly helpful to the team's ability to quickly complete SMA Marshall mix designs and place SMA trial sections.

INITIAL SMA TRIAL SECTIONS

SMA trial sections incorporating two different nominal maximum coarse aggregate sizes - SMA 1 surface course (13 mm) and SMA 2 binder course (19 mm) - were placed in December 1990 on Miller Avenue, an industrial road in Markham (northeast of Toronto). The prime purpose of these first two trial sections was to determine the general applicability of the SMA technology for locally available materials, Marshall method of mix design, production in a conventional hot-mix batch plant and use of standard paving/compaction equipment. Except for minor logistical problems at the plant in handling the filler and fibre addition that were readily overcome, the only significant production problem was ensuring the proper dispersion of the fibre in the SMA mixes.

The aggregates used in the SMA 1 and SMA 2 mixes were 100 percent crushed, quality, locally available aggregates with the gradations given in Table 2 (CA 1, CA 2 and FA 1). SMA mix aggregate and filler compositions were selected to give gradations based on typical grading bands (preliminary specifications) used in Germany, as summarized in Table 2. Standard Marshall mix design procedures [10] were followed using 75 blows per face, as compared to some European experience with 50 blows per face. At this early stage of SMA work there was some concern for potential traffic densification effects and a higher laboratory compaction effort was considered to be prudent. The SMA 1 and SMA 2 mixes were designed at an asphalt cement content giving about 3 percent air voids as indicated in Table 3. While the designs were done with 60/70 penetration polymer (Styrelf) modified asphalt cement, the late season paving work required the use of still available conventional 85/100 penetration grade asphalt cement.

TABLE 2. AGGREGATE GRADATIONS FOR STONE MASTIC ASPHALT (SMA) TRIAL SECTIONS.

SIEVE SIZE	AGGREGATE OR FILLER, PERCENT PASSING (a)						
	CA 1	CA 2	CA 3	FA 1	FA 2	FILLER 1	FILLER 2
26.5 mm	100						
19.0 mm	92.8						
16.0 mm	78.1	100	100				
13.2 mm	59.8	99.5	97.9				
9.5 mm	32.1	75.6	66.1	100	100		
4.75 mm	2.3	4.2	5.3	95.5	90.7		
2.36 mm	1.3	1.2	3.5	66.4	63.8		
1.18 µm	1.1	1.1	3.4	43.8	50.3		
600 µm	0.8	1.0	3.1	31.0	41.6	100	
300 µm	0.7	0.9	2.2	21.7	26.4	98.5	
150 µm	0.5	0.8	1.7	15.4	17.2	94.0	
75 µm	0.4	0.5	1.2	10.4	9.0	86.7	100

a. Description of Aggregates and Fillers (all aggregates 100 percent crushed):

CA 1	Limestone Coarse Aggregate
CA 2	Traprock Coarse Aggregate
CA 3	Dolomitic Sandstone Coarse Aggregate
FA 1	Limestone Screenings Fine Aggregate
FA 2	Dolomitic Sandstone Screenings Fine Aggregate
FILLER 1	Fly Ash Filler
FILLER 2	Ground Dolomite Filler.

The production, placement and compaction of the SMA 1 and SMA 2 mixes is given in Photographs 1 to 3, noting that late season paving was involved with a placement temperature of about 140°C. Extension of the hot-mix batch plant dry mixing time was required to ensure fibre dispersion as uncoated fibre 'balls' were evident in some batches. This was the only significant problem and it is clear that fibre addition for SMA mixes requires special attention.


The general observations on the SMA 1 and SMA 2 trial sections are as follows:

1. SMA mixes have a rich appearance with the aggregate well coated with a thick film of asphalt cement;
2. SMA mixes have an open texture but are not segregated; and
3. uncompacted SMA mix can be laid in thinner lifts than HMA and has greater resistance to roller densification.

TABLE 3. STONE MASTIC ASPHALT (SMA) MIX PROPORTIONS, GRADATIONS AND PROPERTIES.

A. SMA MIX PROPORTIONS, PERCENT (a)					
MATERIAL	DESCRIPTION (SEE TABLE 2)		SMA 1	SMA 2	SMA 3
CA 1	Limestone Coarse Aggregate			40.0	
CA 2	Traprock Coarse Aggregate	65.0	25.0		
CA 3	Dolomitic Sandstone Coarse Aggregate			70.0	
FA 1	Limestone Screenings Fine Aggregate	30.0	30.0		
FA 2	Dolomitic Sandstone Screenings			22.0	
Filler 1	Fly Ash Filler	5.0	5.0		
Filler 2	Ground Dolomite Filler			8.0	
Fibre	Proprietary Glass Fibre	0.3	0.3	0.3	
AC	85/100 Penetration Asphalt Cement	6.5	5.5		
PMA	Polymer (Styrelf) Modified Asphalt Cement			5.3	
B. SMA MIX GRADATIONS, PERCENT PASSING					
SIEVE SIZE	PRELIMINARY SPECIFICATION		TRIAL SECTIONS		
	SURFACE SMA 13 mm	BINDER SMA 19 mm	SMA 1	SMA 2	SMA 3
26.5 mm		100		100	
19.0 mm		95-100		97.1	
16.0 mm		85-95	100	91.2	100
13.2 mm	100	80-90	99.7	83.8	98.5
9.5 mm	75-90	55-75	84.1	66.7	76.3
4.75 mm	29-49	30-50	36.4	35.6	31.7
2.36 mm	22-34	20-35	25.7	25.7	24.5
1.18 mm	16-28	15-30	18.9	18.9	21.4
600 µm	12-24	12-24	15.0	14.9	19.3
300 µm	10-22	10-22	12.0	11.9	15.3
150 µm	9-17	10-18	9.8	9.7	13.0
75 µm	7-12	8-13	7.8	7.7	10.8
C. SMA MIX PROPERTIES					
PROPERTY			SMA 1	SMA 2	SMA 3
Bulk Relative Density			2.445	2.424	2.372
Maximum Relative Density			2.530	2.491	2.471
Air Voids, percent			3.4	2.7	4.0
Voids Mineral Aggregate (VMA), percent			19.0	15.6	15.8
Stability, Newtons at 60°C			9700	13700	8600
Flow, 0.25 mm			25+	25+	25+

a. Fibre and asphalt cement as percent of total mix.

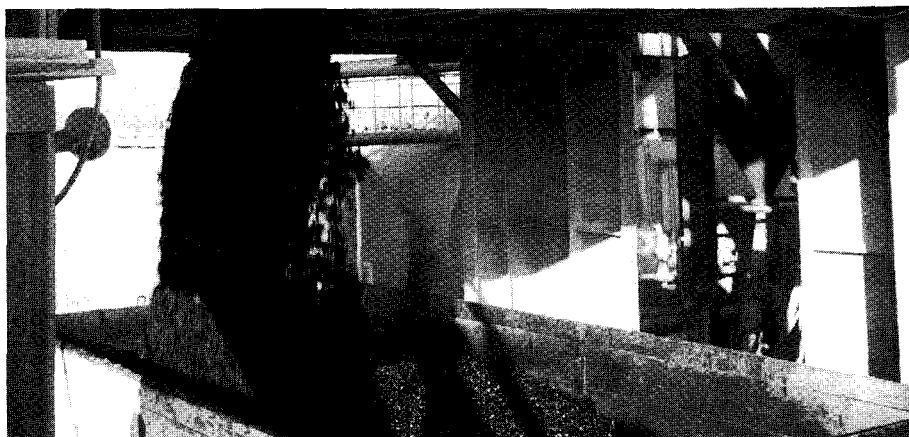

PHOTOGRAPH 1. PRODUCTION OF FIRST ONTARIO STONE MASTIC ASPHALT (SMA 1) IN DECEMBER 1990.

(Conventional hot-mix batch plant with filler in poly-melt bags delivered by belt to weigh hopper/pugmill; fibre in poly-melt bags added into pugmill with increased dry mixing time.)



PHOTOGRAPH 2. PLACING OF STONE MASTIC ASPHALT (SMA 1) IN DECEMBER 1990.

(Conventional paver and static steel-wheel compaction. Ambient temperature about 4°C. No problems were experienced in placing and compacting the SMA 1 and SMA 2 (Table 3) mixes.)



PHOTOGRAPH 3. GENERAL APPEARANCE OF SMA 1 MIX AFTER PLACEMENT AND IN AREA WITH ONE PASS OF STEEL-WHEEL ROLLER.

(The coarse (open) surface texture of the stone mastic asphalt (SMA) is evident after compaction. SMA is very stable with low compaction densification or deformation.)

RUTTING STUDY

In order to evaluate the SMA 1 and SMA 2 trial sections, a series of rutting tests were completed on slabs removed from the test sections. Samples were taken from the centre of the lanes for the SMA 1, SMA 2 and existing pavement (control) sections. The slabs were then tested by the Ontario Ministry of Transportation Bituminous Section (MTO) according to their test procedure "Using a Wheel Tracking Machine for Evaluation of Asphalt Rutting" [11].

The laboratory rutting test is done at a controlled temperature of 60°C using a rubber tired wheel run along the specimen for 4000 cycles (8000 passes). The final rut profile is measured and the average rut depth in millimetres is determined. The temperature is maintained throughout the two hour test by the use of a temperature controlled water bath and infra-red lamps. The specimens are measured across the rut in three places at various stages of the rutting cycles and the average rut depth obtained. The rut depth with number of passes for SMA 1, SMA 2 and control tests are given in Figure 3. The MTO has tentatively set a maximum allowable rut depth of 3.5 mm as the standard for rut resistant mixes. The test data on the three slabs tested indicate the following values:

SMA 1	5.1 mm
SMA 2	6.7 mm
Control	16.8 mm.

Based on the test data presented in Figure 3, it would appear that there was an initial seating of the SMA 1 and SMA 2 specimens prior to the true rutting occurring under the wheel loading. Looking at the plots for both SMA 1 (surface mix) and SMA 2 (binder mix) there appears to have been a seating depth of approximately 3 mm. If this initial seating is accounted for, the SMA 1 and SMA 2 stone mastic mixes meet the MTO criteria. The seating depth translates into a change in compaction from 93 percent (which was achieved in December) and 97 percent which would be more typical under normal paving conditions.

HIGHWAY 7 TRIAL SECTION

While the initial trial section indicated that SMA is somewhat more complicated to produce than HMA, the SMA 1 and SMA 2 trials were considered an overall success. The next step in the SMA technology trials was to refine the Marshall method of SMA mix design and complete a high volume heavy traffic highway trial section. With the assistance of the Ontario Ministry of Transportation, this SMA 3 trial section was completed in June 1991 on Highway 7 north of Toronto.

The SMA 3 mix was designed at 4 percent air voids based on a 50 blows per face Marshall mix design (about 3 percent air voids for 75 blows per face) as there was still a concern with potential overcompaction during rolling and heavy traffic densification. Details on the materials and mix design used for the SMA 3 trial are given in Tables 2 (CA 3 and FA 2) and 3. The placement, compaction and early appearance of the SMA 3 trial sections are shown in Photographs 4,5 and 6 respectively. There was again some problem with glass fibre dispersion and current development work is focusing on other fibres (cellulosic, for instance), fibre dispersion and fibre use in hot-mix drum plants [9].

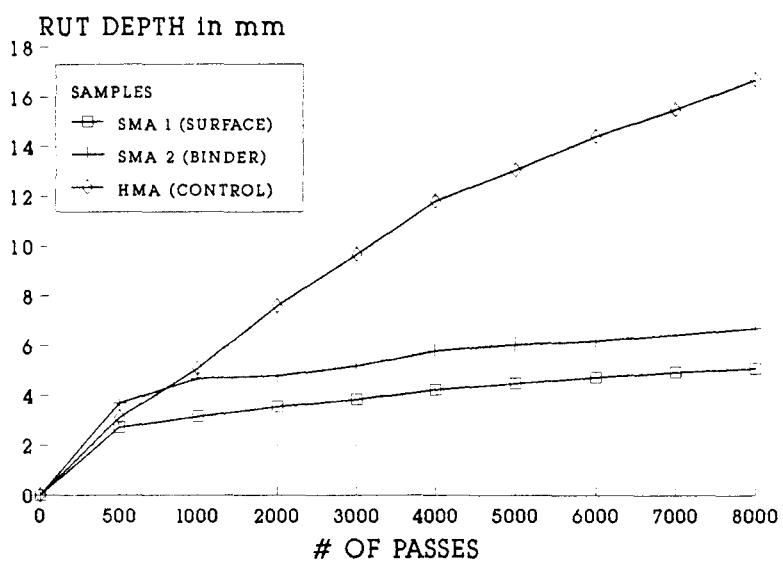


FIGURE 3. RUTTING TEST RESULTS FOR SMA 1 (SURFACE), SMA 2 (BINDER) AND HMA (HOT-MIX ASPHALT SURFACE) PAVEMENT SAMPLES.

(Rutting tests completed by Ontario Ministry of Transportation using their wheel tracking machine [11]. There appears to be an initial 'seating' deformation of about 3 mm at 500 passes for SMA 1 and SMA 2.)

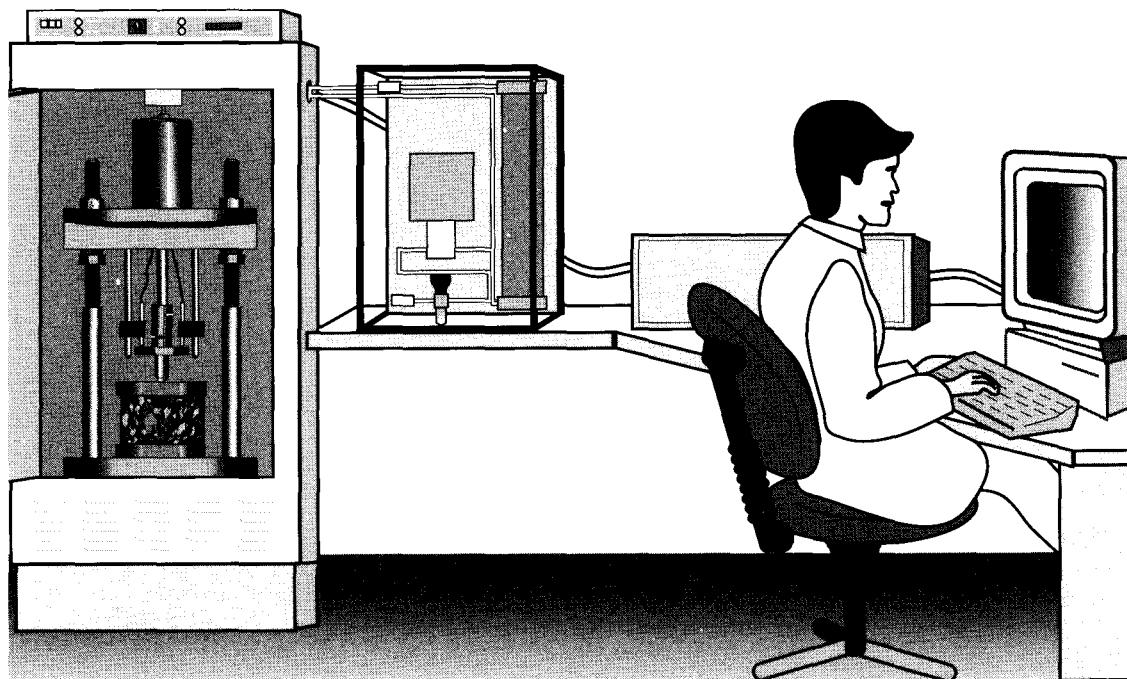



FIGURE 4. SCHEMATIC OF NOTTINGHAM ASPHALT TESTER.

(The Nottingham Asphalt Tester (NAT) is used to measure the mechanical properties of asphalt concrete such as elastic stiffness (resilient modulus) and resistance to permanent deformation [15].)




PHOTOGRAPH 4. PLACING OF STONE MASTIC ASPHALT (SMA 3) TEST SECTION ON HIGHWAY 7 IN JUNE 1991.

(Note the coarse (open) surface texture of SMA 3 on the right compared to the conventional dense friction course (DFC) in the lower left.)

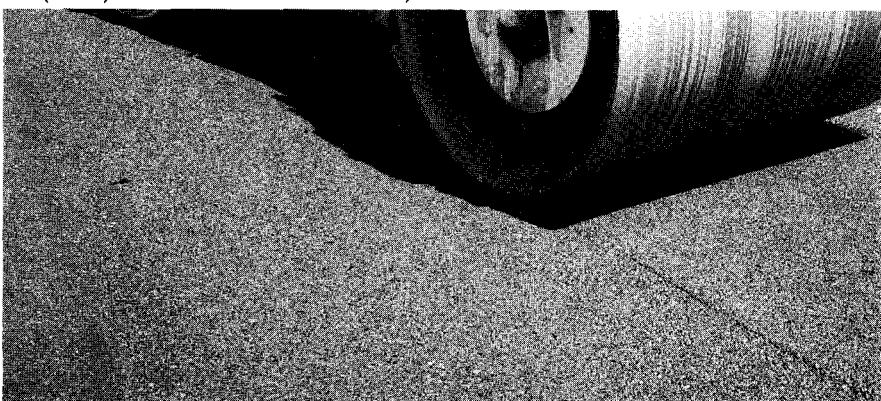


PHOTOGRAPH 5. COMPACTION OF STONE MASTIC ASPHALT (SMA 3) TEST SECTION.

(There were no problems in producing (with extended dry mixing time), placing and compacting the SMA 3 mix. Static steel-wheel compaction is used to avoid potential fracture of coarse aggregate with vibratory compaction and surface flushing of mastic with pneumatic compaction. A soap solution should be used with rollers on SMA mixes containing polymer modified asphalt cement.)

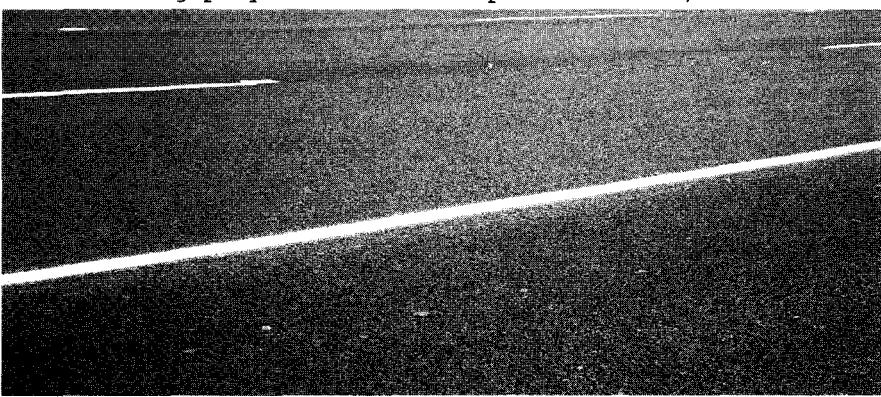

PHOTOGRAPH 6. APPEARANCE OF STONE MASTIC ASPHALT (SMA 3) TEST SECTION AFTER ONE WEEK.

(Note the coarse (open) surface texture of the SMA 3 shoulder and driving lanes in the foreground compared to the conventional dense friction course (DFC) passing lane in the background.)

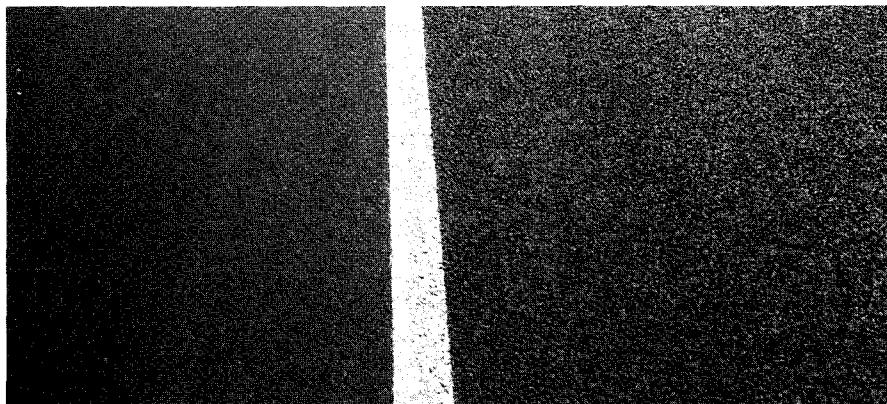

PHOTOGRAPH 7. APPEARANCE OF STONE MASTIC ASPHALT (SMA 3) TEST SECTION COMPARED TO DENSE FRICTION COURSE (DFC) AFTER FIVE WEEKS.

(The coarse (open) surface texture of the SMA 3 driving lane on the right has been maintained under heavy traffic. There has been some surface texture tightening of the DFC passing lane on the left.)



PHOTOGRAPH 8. CLOSE-UP OF STONE MASTIC ASPHALT (SMA 3) SURFACE TEXTURE AFTER FIVE WEEKS.

(The SMA 3 driving lane surface texture has been maintained with no evidence of deformation or mastic flushing.)



PHOTOGRAPH 9. TEST PIECE CUT FROM STONE MASTIC ASPHALT (SMA 3) TEST SECTION.

(Note the stone-to-stone skeleton (Figure 1) in the SMA 3 surface course. The SMA 3 in this area was placed over the cracked existing asphalt concrete courses.)

The early performance of the SMA 3 trial section on Highway 7 has been excellent as shown in Photographs 7 and 8. There has been no tightening on the SMA 3 coarse (open) surface texture, which indicates good resistance to heavy traffic densification. Given the satisfactory compaction achieved with the SMA 3 trial section, apparent lack of traffic densification and current German SMA mix design experience (technical interaction with Wilh. Schütz), a 'standard' SMA Marshall mix design with 50 blows per face at 135°C and design air voids of 3 percent has been adopted for the next SMA highway trial sections.

CURRENT SMA ACTIVITIES

Test cores and sections (Photograph 9) have been taken from the SMA 3 trial section with standard testing, wheel tracking tests (MTO) and mechanical properties characterization in progress. The team is now installing a Nottingham Asphalt Tester (NTA, Figure 4) which will permit the measurement of elastic stiffness (resilient modulus) using the repeated load indirect tension test, resistance to permanent resistance using the uniaxial creep and/or repeated load axial test and fatigue endurance using repeated tension loading [12-15]. This SMA characterization is considered critical to developing the deformation resistance, fatigue endurance and durability of SMA mixes, and such full asphalt concrete characterization is also the focus of current Strategic Highway Research Program Activities [14]. As the structural matrix of SMA mixes is critical to their performance, volumetric methods of optimizing the aggregates selection are also being investigated [16]. Finally, SMA mix designs for three further highway test sections are being finalized and it is anticipated these sections should be completed this year [17].

CONCLUSIONS

While the Ontario technology transfer of SMA is still in progress with a focus on SMA characterization, the trial section results to date must be considered a success. This SMA work, in parallel with current United States SMA test sections, should quickly provide the technical and practical basis for regular SMA use in Ontario.

REFERENCES

1. Kuennen, T., "'Split Mastic' Asphalt - Next Overseas Import?", Roads and Bridges, Vol. 29, No. 1, p. 48, January 1991.
2. Muri, W., "Paving the Way", TR News, No. 154, p. 2, Transportation Research Board, Washington, May-June 1991.
3. Emery, J.J., "Stone Mastic Asphalt - Ontario Looks Closer at New High-Performance Pavement Mixes", AsphaltTopics, p. 3, Ontario Hot Mix Producers Association, Mississauga, July 1991.
4. Anon, "U.S. Road Builders Look to Europe", ENR, Vol. 227, No. 6, p. 8, August 12, 1991.
5. FHWA, Stone Mastic Asphalt - SMA - Technology Synopsis and Work Plan, Draft, Federal Highway Administration, Washington, February 1991.
6. AASHTO, 1990 European Asphalt Study Tour, American Association of State Highway and Transportation Officials, Washington, June 1991.
7. FHWA, "Bituminous Mix Design and Field Control", Technical Advisory T5040.24, Federal Highway Administration, Washington, August 22, 1985.
8. EAPA, Porous Asphalt and Stone Mastic Asphalt Surface Layers in the EAPA Countries, European Asphalt Pavement Association, Stockholm, May 1989.
9. ScanRoad, An Introduction to Stone Mastic Asphalt (SMA), ScanRoad, Waco, January 1991.
10. AI, "Mix Design Methods for Asphalt Concrete and Other Hot-Mix Types", Manual Series No. 2, Asphalt Institute, Lexington, 1988.
11. Yacyshyn, R., Tam, K.K. and Lynch, D.F., "Using a Wheel Tracking Machine for Evaluation of Asphalt Rutting", Report EM-93, Engineering Materials Office, Ontario Ministry of Transportation, Downsview, March 1989.
12. Brown, S.F., "Improving Asphalt Technology for Roads", Municipal Engineer, Vol. 6, No. 2, p. 29, February 1989.
13. Shell, "Mechanical Testing of Bituminous Mixes", The Shell Bitumen Handbook, p. 223, Shell Bitumen U.K., Chertsey, 1990.
14. Harrigan, E., "Asphalt Mixture Specification Targeted at Reduction of Cracks, Ruts, Potholes", Focus, p. 1, Strategic Highway Research Program, Washington, August 1991.
15. Cooper, The Nottingham Asphalt Tester, Cooper Research Technology Limited, Horsley, 1991.
16. Ramljak, Z. and Emery, J.J., "Spatial Design of Optimal Asphalt Mixes", Proceedings of the Canadian Technical Asphalt Association 34th Annual Conference, p. 324, Halifax, November 1989.
17. MTO, "Stone Mastic Asphalt for Tougher Pavements", R and D Reports, Vol. 3, No. 3, p. 1, Ontario Ministry of Transportation, Downsview, August 1991.